

Ultrafast nonlinear optical tuning of photonic crystal cavities

Ilya Fushman,^{a)} Edo Waks,^{b)} Dirk Englund,^{c)} Nick Stoltz,^{d)} Pierre Petroff,^{d)} and Jelena Vučković^{e)}

E. L. Ginzton Laboratory, Stanford University, Stanford, California 94305

(Received 22 November 2006; accepted 26 January 2007)

The authors demonstrate fast (up to 20 GHz), low-power (60 fJ, 3 ps pulses) modulation of photonic crystal cavities in GaAs containing InAs quantum dots. Rapid modulation through blueshifting of the cavity resonance is achieved via free-carrier injection by an above-band picosecond laser pulse. Slow tuning by several linewidths due to laser-induced heating is also demonstrated. © 2007 American Institute of Physics. [DOI: 10.1063/1.2710080]

Nonlinear optical switching in photonic networks is a promising approach for ultrafast low-power optical data processing and storage.¹ In addition, optical data processing will be essential for optics-based quantum information processing systems. A number of elements of an all-optical network have been proposed and demonstrated in silicon photonic crystals.^{2,3} Tuning of the photonic crystal lattice modes has also been demonstrated.^{4,5} Here, we directly observe ultrafast (≈ 20 GHz) nonlinear optical tuning of photonic crystal (PC) cavities containing quantum dots (QDs). We perform the fast tuning via free-carrier injection, which alters the cavity refractive index, and observe it directly in the time domain. Three material effects can be used to quickly alter the refractive index. First is the index change due to free-carrier (FC) generation, which is discussed in this work, and has been explored elsewhere.⁴ The cavity resonance shifts to shorter wavelengths due to the free-carrier effect. Switching via free-carrier generation is limited by the lifetime of free carriers and depends strongly on the material system and geometry of the device. In our case, the large surface area and small mode volume of the PC reduce the lifetime of free carriers in GaAs. Free carriers can alternatively be swept out of the cavity by applying a potential across the device.⁶ The second effect that can be used to modify the refractive index is the Kerr effect, which is promising for a variety of other applications^{7,8} and, in principle, should result in modulation rates of 10^{15} – 10^{16} Hz. However, the free-carrier effect is more easily achieved in the GaAs PC considered here. The third effect is thermal tuning (TT) via optical heating of the sample through absorption of the pump laser. This process is much slower than free-carrier and Kerr effects and shifts the cavity resonance to longer wavelengths due to the temperature dependence of the refractive index. The time scale for this process is on the order of microseconds. Here we consider these two processes for modulating cavity resonances and focus on the higher-speed FC tuning.

Photonic crystal samples investigated in this study are grown by molecular beam epitaxy on a Si *n*-doped GaAs (100) substrate with a 0.1 μm buffer layer. The sample con-

tains a ten period distributed Bragg reflector (DBR) mirror consisting of alternating layers of AlAs/GaAs with thicknesses of 80.2/67.6 nm, respectively. A 918 nm sacrificial layer of $\text{Al}_{0.8}\text{Ga}_{0.2}\text{As}$ is located above the DBR mirror. The active region consists of a 150 nm thick GaAs region with a centered InGaAs/GaAs QD layer. QDs self-assemble during epitaxy operating in the Stranski-Krastanov growth mode. InGaAs islands are partially covered with GaAs and annealed before completely capping with GaAs. This procedure blueshifts the QD emission wavelengths⁹ towards the spectral region where Si-based detectors are more efficient.

PC cavities, such as those shown in Fig. 1, were fabricated in GaAs membranes using standard electron beam lithography and reactive ion etching techniques. Finite difference time domain (FDTD) simulations predict that the fundamental resonance in the cavity has a field maximum in the high index region (Fig. 1), and thus a change in the value of the dielectric constant should affect these modes strongly. We investigated the dipole cavity (Fig. 1), the linear three-hole defect cavity,¹⁰ and the linear two-hole defect cavity designs. The experimentally observed Q 's for all three cavities were in the range of 1000–2000 (optimized cavities can have much higher Q 's), and consequently the experimental

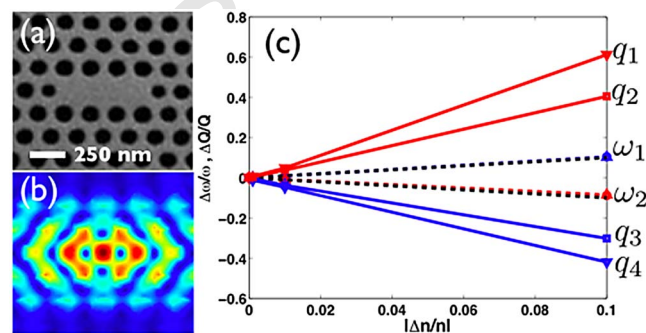


FIG. 1. (Color online) (a) Scanning electron micrograph of the L3-type cavity. (b) High- Q mode electric field amplitude distribution, as predicted by FDTD simulations. (c) FDTD simulations of frequency and Q changes as $\Delta n/n$ changes from $\pm 10^{-3}$ to $\pm 10^{-1}$. A high- Q ($Q_{\text{HQ}}=20000$) and low- L ($Q_{\text{LQ}}=2000$) cavity were tuned: (q_1) $\Delta Q/Q$ for $\Delta n > 0$ and $Q=Q_{\text{HQ}}$, (q_2) $\Delta Q/Q$ for $\Delta n > 0$ and $Q=Q_{\text{LQ}}$, (ω_1) $\Delta\omega/\omega$ for $\Delta n < 0$, (ω_2) $\Delta\omega/\omega$ for $\Delta n > 0$ for both high Q and low Q modes, (q_3) $\Delta Q/Q$ for $\Delta n < 0$, $Q=Q_{\text{LQ}}$, and (q_4) $\Delta Q/Q$ for $\Delta n < 0$, $Q=Q_{\text{HQ}}$. The lines $\Delta n/n$ for $\Delta n > 0$ and $\Delta n < 0$ (black dotted lines) are also plotted and overlap exactly with the lines $\Delta\omega/\omega$ labeled ω_2 and ω_1 . As can be seen, the magnitude of the relative frequency change is independent of Q , but the higher Q cavity is degraded more strongly by the change in index. For an increase in n , the Q increases due to stronger total internal reflection confinement in the slab, as expected.

^{a)}Also at Department of Applied Physics, Stanford University. Electronic mail: ifushman@stanford.edu

^{b)}Also at Department of Electrical and Computer Engineering, University of Maryland, College Park, MD 20742.

^{c)}Also at Department of Applied Physics, Stanford University.

^{d)}Also at Department of Electrical and Computer Engineering, University of California Santa Barbara, CA 93106.

^{e)}Also at Department of Electrical Engineering, Stanford University.

tuning results were similar for all three cavities.

Photonic crystal cavities were made to spectrally overlap with the QD emission, and are visible above the QD emission background due to an increased emission rate and collection efficiency of dots coupled to the cavity. Quantum dot emission was excited with a Ti:sapphire laser tuned to 750 nm in a pulsed or cw configuration. In the pulsed mode, the pump produced 3 ps pulses at an 82 MHz repetition rate. Tuning was achieved by pulsing the cavity with appropriate pump power. The cavity emission was detected on a spectrometer and on a streak camera for the time resolved measurements.

Tuning is achieved by quickly changing the value of the dielectric constant $\epsilon = n^2$ of the cavity with a control pulse. The magnitude of the refractive index shift Δn can be estimated from

$$\frac{\Delta\omega}{\omega} \approx -\frac{1}{2} \frac{\int \Delta\epsilon |E|^2 dV}{\int \epsilon |E|^2 dV} \approx -\frac{\Delta n}{n}. \quad (1)$$

Above, ω is the resonance of the unshifted cavity, $|E|^2$ is the amplitude of the cavity mode, and the integral goes over all space. In order to shift by a linewidth, we require $\Delta\omega/\omega = 1/Q$, which gives $\Delta n = n/Q$. FDTD calculations indeed verify that for a linear cavity with Q , 1000, a $\Delta n \approx 10^{-2}$ shifts the resonance by more than a linewidth, as seen in Fig. 1.

As described above, two tuning mechanisms were investigated in this work. The first is temperature tuning, which is quite slow (on the time scale of microseconds). The second is the free-carrier-induced refractive index change, which is found to occur on the time scale of tens of picoseconds. Therefore, we can look at the two effects separately in the time domain.

In the case of FC tuning only,

$$\frac{\Delta n(t)}{n} = \frac{\Delta n_{\text{FC}}(t)}{n} = \eta N_{\text{FC}}(t), \quad (2)$$

where $N_{\text{FC}}(t)$ is the density of free carriers in the GaAs slab, and the value of η is given in terms of fundamental constants (ϵ_0, c), dc refractive index (n_0), charge (e), effective electron mass (m_e^*), and wavelength (λ) as $\eta = -e^2 \lambda^2 / 8 \pi^2 c^2 \epsilon_0 n_0 m_e^*$,¹¹ and we calculate $\eta \approx 10^{-21} \text{ cm}^3$ for our system.

The FC density changes with the pump photon number density $P(t)$, with pulse width τ_p , in time t as

$$\frac{dN_{\text{FC}}}{dt} = -\frac{1}{\tau_{\text{FC}}} N_{\text{FC}} + \frac{P(t)}{\tau_p}. \quad (3)$$

The carriers decay with $1/\tau_{\text{FC}} = 1/\tau_r + 1/\tau_{\text{nr}} + 1/\tau_c$, where τ_r and τ_{nr} are the radiative and nonradiative recombination times of free carriers, and τ_c is the relaxation time (or capture time) into the QDs. While $\tau_c \approx 30\text{--}50 \text{ ps} \ll \tau_r, \tau_{\text{nr}}$, the dot capture is not the dominant relaxation process. The dots saturate for the duration of the dot recombination lifetime $\tau_d \approx 200 \text{ ps--}1 \text{ ns}$, and because the dot density is much smaller than the FC density, the effective capture time is much longer. Qualitatively, we can describe this effect by lengthening τ_c by a factor $1/x$ as $\tau_c \rightarrow \tau_c/x \ll \tau_r, \tau_{\text{nr}}$, where $x \ll 1$ is essentially the ratio of QD to FC densities. The FC density is then given by

$$N_{\text{FC}}(t) = N_{\text{FC}}(0)e^{-t/\tau_{\text{FC}}} + e^{-t/\tau_{\text{FC}}} \int_0^t e^{t'/\tau_{\text{FC}}} \frac{P(t')}{\tau_p} dt'. \quad (4)$$

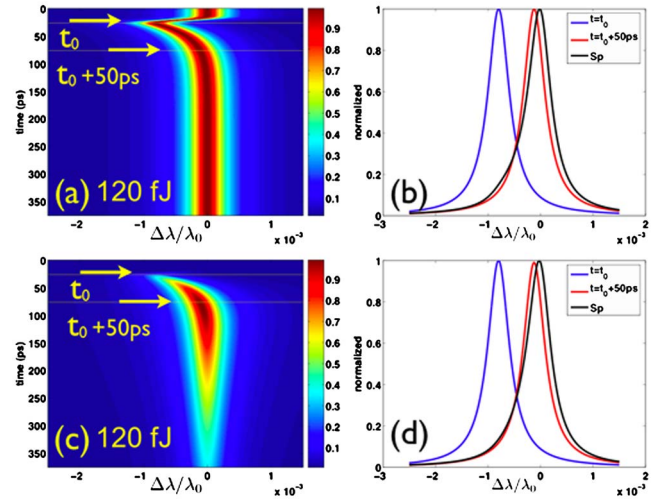


FIG. 2. (Color online) Numerical model of a free-carrier tuned cavity. In (a), the cavity is always illuminated by a light source. Panel (b) shows the cavity resonance at the peak of the free-carrier distribution ($t=0$) and 50 ps later, as indicated by the yellow arrows in (a). The time-integrated spectrum is shown as the asymmetric black line (labeled Sp) in (b), and corresponds to the signal seen on the spectrometer, which is the integral over the whole time window of the shifted cavity. The asymmetric spectrum indicates shifting. In (c) and (d) the same data are plotted, but now we consider the cavity illuminated only by QD emission with a turn-on delay of 30 ps due to the carrier capture lifetime τ_c , and a QD lifetime of 200 ps. In (d), the asymmetry of the line is even smaller in this case.

In order to shift the cavity resonance by a linewidth ($\Delta n/n = 10^{-3}$), we need $N_{\text{FC}} \approx 10^{18} \text{ cm}^{-3}$ according to Eq. (2). However, since our coupling efficiency is not perfect, we take into account the GaAs absorption coefficient $\alpha \approx 10^4 \text{ cm}^{-1}$, reflection losses from the 160 nm GaAs membrane ($R = (n_{\text{air}} - n_{\text{GaAs}})^2 / (n_{\text{air}} + n_{\text{GaAs}})^2 \approx .3$), lens losses (50%), and an approximately $5 \mu\text{m}$ spot size. With these values, powers as low as 12–120 fJ in a 3 ps pulse should yield the desired shifts of order $\Delta n/n \approx 10^{-3}$.

In our experiment, we monitor the cavity resonance during the tuning process using QD emission. Thus, we need to account for the delay between the pump and onset of emission in QDs. The QDs are excited by free carriers according to

$$\frac{dN_{\text{QD}}}{dt} = -\frac{1}{\tau_d} N_{\text{QD}} + \frac{N_{\text{FC}}}{\tau_c}. \quad (5)$$

Thus the QD population (assuming no excited dots at carriers at $t=0$) is given by

$$N_{\text{QD}}(t) = \frac{e^{-t/\tau_{\text{QD}}}}{\tau_p \tau_c} \int_0^t e^{t'((1/\tau_{\text{QD}}) - (1/\tau_{\text{FC}}))} \int_0^{t'} e^{t''/\tau_{\text{FC}}} P(t'') dt'' dt', \quad (6)$$

where τ_p is the pump pulse width, $\tau_{\text{QD}} \approx 200 \text{ ps}$ is the average cavity coupled QD lifetime, $\tau_{\text{FC}} \approx 30 \text{ ps}$ is the FC lifetime, and $P(t)$ is the pump photon number density. The observed spectrum is that of a Lorentzian with a time-varying central frequency $\omega_0(t)$ (for simplicity, we assume that the Q factor is time invariant), which we define as

$$S(\omega, t) = \left(1 + 4Q^2 \left(1 - \frac{\omega_0^2(t)}{\omega^2} \right) \right)^{-1}. \quad (7)$$

The numerical results are shown in Fig. 2. We find that

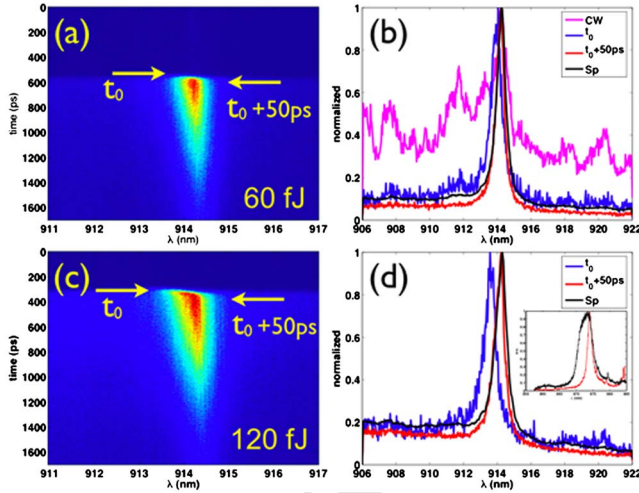


FIG. 3. (Color online) Experimental result of FC cavity tuning for the L3 cavity. Panels (a) and (b) show wavelength vs time plots of the cavity, as it is pumped. Panels (c) and (d) show normalized spectra of the cavity taken at different time points from the data in (a) and (b). In (a), the cavity is always illuminated by a light source and pulsed with a 3 ps Ti:sapphire pulse. Panel (b) shows the normalized cavity spectrum at the peak of the FC distribution ($t=0$) and 50 ps later, as indicated by the yellow arrows in (a). In order to verify that the cavity tunes at the arrival at the pulse, we combine the pulsed excitation with a weak cw above-band pump. The emission due to the cw source is always present, and this very weak emission is reproduced in panel (b) as the broad background with a peak at the cold cavity resonance in (b). The time-integrated spectrum is shown as the black line (spectrometer) in (b). In (c) and (d) the same data are plotted, but now we consider the cavity illuminated only by QD emission pulsed by 120 fJ and 3 ps pulses from the Ti:sapphire source. In (d), suppression by about 0.4–0.35 at the cold cavity resonance can be seen. The inset shows a strongly asymmetric spectrum of a dipole-type cavity under excitation of 1.2 pJ and the same cavity at low power after prolonged excitation. Such strong excitation degrades the Q .

going beyond 120 fJ (10 μ W average power) does not result in a larger shift, but destroys and shifts the cavity Q permanently.

The experimental data are shown in Fig. 3. We used moderate energy pulses (≈ 120 fJ) to shift the cavity by one-half linewidth. Stronger excitation results in higher shifts as indicated by an extremely asymmetric spectrum shown on the inset in (d) of Fig. 3, where 1.4 pJ were used. However, prolonged excitation at this power leads to a sharp reduction in Q over time.

In the case of TT,

$$\frac{\Delta n(t)}{n} = \beta T. \quad (8)$$

Continuous wave above-band excitation of the sample results in both free-carrier generation and heating. In this case, the heating mechanism dominates, and the cavity redshifts. The predominant effect on the dielectric constant is the change in the band gap with temperature due to lattice expansion and phonon population. The cavity itself could potentially expand, but since the thermal expansion coefficient of GaAs is on the order of 10^{-6} K $^{-1}$, this is insignificant. As the cavity redshifts, the Q first increases due to gain and then drops due to absorption losses. The experimental data for thermal tuning are shown in Fig. 4. From a fit to the frequency shift, we obtain $\beta T/P_{in} \approx 3 \times 10^{-3}$.

In conclusion, we show that fast (20 GHz) tuning of GaAs cavities can be realized with small pulse energies of

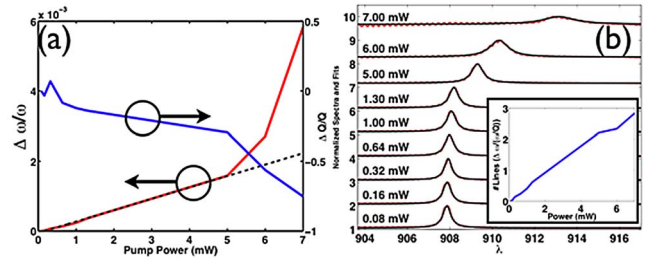


FIG. 4. (Color online) Thermal tuning of the L3 cavity under cw excitation. (a) Measured $\Delta\omega/\omega$ (left axis) and $\Delta Q/Q$ (right axis) as a function of pump power for the L3 cavity, obtained from the fits to the spectra shown in (b). The Q initially increases due to moderate gain and then degrades, while ω shifts linearly. The straight dashed line fits $\Delta\omega/\omega = 3 \times 10^{-3} \times P_{in} - 5 \times 10^{-5}$ with 95% confidence and with root mean square deviation of ≈ 0.99 . At very high power, the change in frequency does not follow the same trend. The inset in (b) shows a plot of $\Delta\omega/(\omega/Q)$, which is a measure of the number of lines that we shift the cavity by. A shift of three linewidths is obtained.

60–120 fJ. The quoted energies are larger than the actual energies needed for switching, as a result of the losses in optics and imperfect coupling. In the ideal coupling case and absence of losses, switching with energies as low as 0.36 fJ can be obtained. Under these conditions the cavity is shifted by almost a linewidth, which leads to suppression of transmission at the cold cavity frequency by $\approx 1/e$. The suppression depends on the Q of the cavity and for cavities with $Q \approx 4000$, shifts by a full linewidth would be obtained. Thus, fast control over photon propagation in a GaAs based PC network is easily achieved and can be used to control the elements of an optical or quantum on-chip network. Free-carrier tuning strongly depends on the geometry of the cavity, since a larger surface area leads to a shorter FC lifetime. Thus, our future work will focus on identifying optimal designs for shifting and a demonstration of an active switch based on the combination of PC cavities and wave guides. Our ultimate goal is all-optical logic with photon packets on the chip.

Financial support was provided by the MURI Center for photonic quantum information systems (ARO/DTO Program No. DAAD19-03-1-0199), ONR Young Investigator Award, and NSF Grant No. CCF-0507295. Two of the authors (I.F. and D.E.) would like to thank the NDSEG fellowship for financial support.

¹M. Soljacic and J. Joannopoulos, *Nature (London)* **3**, 211 (2004).
²A. Shinya, S. Mitsugi, T. Tanabe, M. Notomi, I. Yokohama, H. Takara, and S. Kawarishi, *Opt. Express* **14**, 1230 (2006).
³T. Tanabe, M. Notomi, S. Mitsugi, A. Shinya, and E. Kuramochi, *Appl. Phys. Lett.* **87**, 15112 (2005).
⁴A. D. Bristow, J.-P. R. Wells, W. H. Fan, A. M. Fox, M. S. Skolnick, D. M. Whittaker, J. S. Roberts, and T. F. Krauss, *Appl. Phys. Lett.* **83**, 851 (2003).
⁵P. M. Johnson, A. F. Koenderink, and W. L. Vos, *Phys. Rev. B* **66**, 081102 (2002).
⁶H. Rong, R. Jones, A. Liu, O. Cohen, D. Hak, A. Fang, and M. Paniccia, *Nature (London)* **433**, 725 (2005).
⁷M. Hochberg, T. Baehr-Jones, G. Wang, M. Shearn, K. Harvard, J. Luo, B. Chen, Z. Shi, R. Lawson, P. Sullivan, A. Jen, L. Dalton, and A. Scherer, *Nat. Mater.* **5**, 703 (2006).
⁸I. Fushman and J. Vučković, e-print quant-ph/0603150.
⁹P. M. Petroff, A. Lorke, and A. Imamoglu, *Phys. Today* **46**(5), 54 (2001).
¹⁰Y. Akahane, T. Asano, B.-S. Song and S. Noda, *Nature (London)* **425**, 944 (2003).
¹¹B. Bennett, R. Soref, and J. Del-Alamo, *IEEE J. Quantum Electron.* **36**, 113 (1990).